

# VITRON IG-2 – discover the Original

Our glass IG-2 features excellent transmittance and low thermal change in refractive index and dispersion.

IG-2 is ideal for applications in combination with other IR material for color corrected designs and infrared optical systems without thermal defocusing in the 2-12 μm spectrum.

Molding, classical polishing or Single-Point-Diamond-Machining permits the production of optical components with flat, spherical and/or aspherical shaped surfaces for the Infra-Red and Optoelectronics industries.

Antireflection coatings further improve transmission by reducing the reflection at the air-glass interfaces.

VITRON currently produces 5 different types of Chalcogenide Glass that are applicable to optics and optoelectronics system design.




Typical delivery in form of blanks:

- ∅ 5 – 150 mm
- 5 – 100 mm
- ct 0.8 – 150 mm

## Index of Refraction (@ 20°C)

λ [μm]	n(λ)
1.00	2.5969
1.50	2.5462
2.00	2.5298
3.00	2.5180
4.00	2.5133
5.00	2.5104
6.00	2.5078
7.00	2.5054
8.00	2.5026
9.00	2.4999
10.00	2.4968
11.00	2.4931
12.00	2.4891

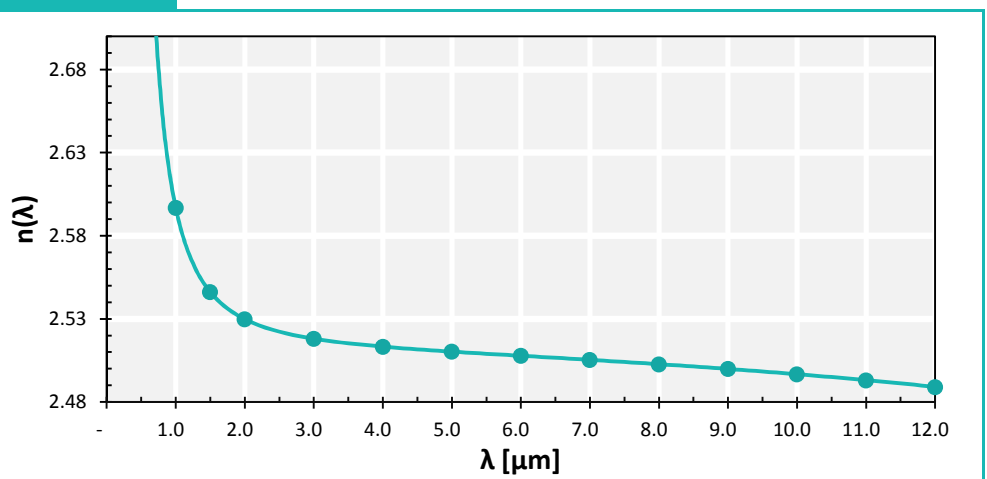

## Sellmeier-Coefficients (@ 20°C)

<b>A</b>	3.3414
<b>B<sub>1</sub></b>	2.9621
<b>C<sub>1</sub></b>	0.3600
<b>B<sub>2</sub></b>	0.8310
<b>C<sub>2</sub></b>	35.0233

$$n^2(\lambda) = A + \frac{B_1 \lambda^2}{\lambda^2 - C_1^2} + \frac{B_2 \lambda^2}{\lambda^2 - C_2^2}$$

## Dispersion (@ 20°C)

λ [μm]	v <sub>λ</sub>
4.00	199
10.00	111

$$v_4 = \frac{n_4 - 1}{n_3 - n_5}$$

$$v_{10} = \frac{n_{10} - 1}{n_8 - n_{12}}$$


## Thermo-Optical Coefficient (@ 20°C)

λ [μm]	dn/dT [×10 <sup>-6</sup> /K]
3.40	67.7
10.60	67.2

# VITRON IG-2 – discover the Original

## Transmission

$\lambda$ [ $\mu\text{m}$ ]	$T(\lambda)$ [%]
1.00	60.5
1.50	65.4
2.00	66.3
3.00	65.9
4.00	66.9
5.00	67.0
6.00	68.1
7.00	68.1
8.00	67.2
9.00	68.8
10.00	68.7
11.00	65.6
12.00	39.4
13.00	27.4
14.00	49.0

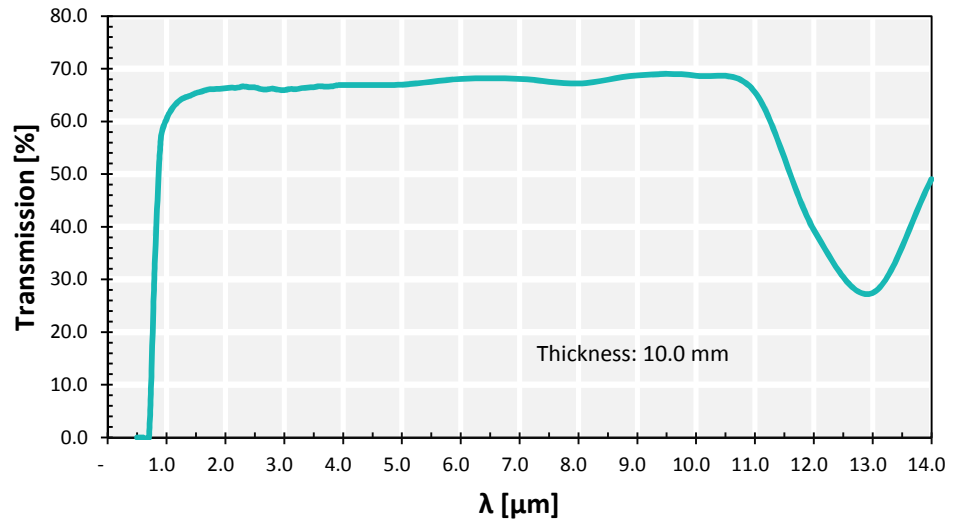

## Material Properties

	$\text{Ge}_{33}\text{As}_{12}\text{Se}_{55}$	
Composition		
Density	4.41	$\text{g}\cdot\text{cm}^{-3}$
Thermal Expansion (20°C – 100°C)	12.1	$\times 10^{-6} \text{K}^{-1}$
Specific Heat Capacity	0.33	$\text{J}\cdot\text{g}^{-1}\cdot\text{K}^{-1}$
Thermal Conductivity	0.24	$\text{W}\cdot\text{m}^{-1}\cdot\text{K}^{-1}$
Transition Temperature	368	°C
Softening Point	445	°C
Young's Modulus	21.5	GPa
Modulus of Rupture	19	MPa
Shear Modulus	8.9	GPa
Hardness (Knoop)	1.41	GPa

## Chemical Properties

The VITRON chalcogenid glasses are insoluble in water. Under normal circumstances, no reactions are observed between glass and organic solvents.

## Typical Forms of Supply

Our chalcogenid glasses are fine-annealed with 3.75 K/h. Variability of the index of refraction: between charges  $\leq 10^{-3}$   
within a charge  $\leq 10^{-4}$

Semi-finished: Boules, Blanks in disk and rectangular shapes, Rods  
Other shapes by customer request

Optical components: Windows, Lenses, Prisms and other optical parts according to customer specification  
AR/AR coatings on customer request

**VITRON**  
Spezialwerkstoffe GmbH  
Maau  
Am Naßtal 5  
D-07751 Jena

Phone: +49-(0)3641-2 88 1-30  
Fax: +49-(0)3641-2 88 1-55  
Email: kontakt@vitron.de  
Internet: www.vitron.de

**VITRON**  
Your Material Specialist